

LAPPEENRANNAN-LAHDEN TEKNILLINEN YLIOPISTO LUT  
LUT School of Energy Systems  
Degree Programme in Environmental Technology  
Bachelor's Thesis

**COMPARISON OF FORMALDEHYDE EMISSIONS DETERMINA-  
TION IN LIGNIN- AND PHENOLIC -BASED RESINS IN PLYWOOD  
PANELS**

Examiner: Professor, Risto Soukka

Instructor: Associate Professor, Sanni Väisänen

Business Development Manager, Heidi Suomela-Uotila

Business Development Manager, Suvi Pietarinen

Lappeenranta 22.4.2021

Sandra Järv

## TIIVISTELMÄ

Lappeenranta-Lahti University of Technology LUT  
LUT School of Energy Systems  
Ympäristötekniikan koulutusohjelma

Sandra Järv

### **Vaneriteollisuuden formaldehydipäästöjen mittausmenetelmien vertailu ligniini- ja fenolipohjaisilla hartseilla**

Kandidaatintyö, 2021

31 sivua, 11 kuvaa, 10 taulukkoa ja 5 liitettä

Tarkastajat: Professor, Risto Soukka  
Ohjaajat: Associate Professor, Sanni Väisänen  
Business Development Manager, Heidi Suomela-Uotila  
Business Development Manager, Suvi Pietarinen

Hakusanat: ligniini-fenoli-formaldehydi hartsi, ligniini, vaneri, formaldehydipäästöt, kaasuanalysaattori, eksikaattorimenetelmä

Tässä kandidaatintyössä tutkitaan formaldehydipäästöjä mittaavien kaasuanalysaattorin sekä eksikaattorimenetelmien korrelaatiota. Tämän lisäksi työssä vertaillaan ligniini- sekä fenolipohjaisten hartsiin formaldehydipäästöjä. Katsaus keskittyy vanerituotantoon ja tutkimus tehdään yhteistyössä UPM Biochemicalsin kanssa. Tällä hetkellä eksikaattorimenetelmällä mitatuille formaldehydipäästöille ei ole EN-standardia. Mittausmenetelmien välisen korrelaatiokertoimen avulla voitaisiin hyödyntää tätä kustannustehokasta ja helposti toteutettavaa mittausmenetelmää. Ligniini- ja fenolipohjaisten hartsiin tutkimuksella kartoitetaan tulevaisuuden mahdollisuuksia formaldehydipäästöjen pienentämiseksi. Hartsityypin lisäksi kandidaatintyössä tutkitaan myös puulajin, liimanlevityksen sekä puristusajan vaikutusta formaldehydipäästöihin.

Kaasuanalysaattorin sekä eksikaattorimenetelmän tulosten välillä ei havaittu lineaarista korrelaatiota. Puulajin vaikutus formaldehydipäästöihin vahvistettiin, ja todettiin, että lehtipuut emittoivat vähemmän formaldehydiä kuin havupuut. Liimanlevityksellä ja puristusajalla ei havaittu olevan suoraa vaikutuksia päästöihin. Myöskään hartsin ligniinimäärällä ei todettu olevan vähentävää vaikutusta vanerin formaldehydipäästöihin.

## **ABSTRACT**

Lappeenranta-Lahti University of Technology LUT  
LUT School of Energy Systems  
Degree Programme in Environmental Technology

Sandra Järv

### **Comparison of formaldehyde emissions determination in lignin- and phenolic -based resins in plywood panels**

Bachelor's thesis, 2021

31 pages, 11 charts, 10 tables and 5 appendices

Examiner: Professor, Risto Soukka  
Instructor: Associate Professor, Sanni Väisänen  
Technical Sales Manager, Heidi Suomela-Uotila  
Business Development Manager, Suvi Pietarinen

Keywords: lignin-phenol-formaldehyde resin, lignin, plywood, formaldehyde emissions, gas analysis method, desiccator method

In this bachelor's thesis, correlation for formaldehyde emission release measurements of gas analysis method and desiccator method was calculated. Also, formaldehyde emissions of lignin- and phenolic -based resins were compared. The study concentrated on the plywood panels and was carried out in cooperation with UPM Biochemicals. The correlation between methods was calculated for predicting the results. Today there is no EN-standard for formaldehyde emission limit values for plywood panels measured by desiccator method. Lignin- and phenolic -based resins were compared to study the future possibilities for formaldehyde emissions reduction. Other parameters studied in this thesis affecting the formaldehyde release were wood species, glue factor, and pressing time.

No linear correlation was found between the gas analysis method and desiccator method. It was confirmed that wood species tend to have an impact on the formaldehyde emissions in the panel. Hardwood emits less formaldehyde than softwood as it was predicted. Glue factor and pressing time were not detected to have a clear impact on the emissions. Also, the amount of lignin did not appear to reduce the formaldehyde emission from plywood panels.

## TABLE OF CONTENTS

LIST OF SYMBOLS .....	5
1 INTRODUCTION .....	6
2 PLYWOOD PANELS AND RESINS .....	7
2.1 Plywood.....	7
2.2 Phenol-formaldehyde resin .....	7
2.3 Lignin .....	8
2.4 Lignin-phenol-formaldehyde resin.....	9
3 FORMALDEHYDE EMISSIONS .....	11
3.1 Formaldehyde.....	11
3.2 Guidelining the emissions .....	12
3.3 Methods for reducing the emissions .....	13
4 DETERMINATION METHODS .....	16
4.1 Gas analysis method.....	16
4.2 Desiccator method.....	17
5 ANALYZING METHODS AND ERROR ESTIMATION .....	19
5.1 Correlation between methods.....	19
5.2 Adjustments for FE reduction .....	19
5.3 Error estimation.....	20
6 RESULTS .....	22
6.1 Comparing testing methods.....	22
6.2 Comparing the emissions of PF and LPF resins .....	25
7 CONCLUSIONS .....	29
8 SUMMARY .....	31
REFERENCES .....	32

## APPENDICES

Appendix I. Description of the test pieces.

Appendix II. Calculation of the expanded uncertainty, gas analysis.

Appendix III. Calculation of the expanded uncertainty, desiccator method.

Appendix IV. Correlation between FE and glue factor.

Appendix V. Correlation between FE and pressing time.

## LIST OF SYMBOLS

$A$	area	[m <sup>2</sup> ]
$d_i$	spread	-
$d_{ri}$	percentage spread	[%]
$k$	coverage factor	-
$l_x$	width length	[m]
$l_y$	width height	[m]
$l_z$	width depth	[m]
$n$	number of replicates	-
$R^2$	correlation coefficient	-
$s_{ri}$	random error	[%]
$U$	expanded uncertainty	[%]
$\bar{x}$	average	-

## Abbreviations

CO <sub>2</sub>	carbon dioxide
FE	formaldehyde emissions
GHG	greenhouse gas
IARC	International Agency for Research on Cancer
LPF	lignin-phenol-formaldehyde
NaOH	sodium hydroxide
Na <sub>2</sub> S	sodium sulfide
PF	phenol-formaldehyde
ppb	parts per billion
UF	urea-formaldehyde
VOC	volatile organic compound
WBP	wood-based panel
WHO	World Health Organization

## 1 INTRODUCTION

Formaldehyde is a pungent smelling, colorless compound, which is mainly used in producing resins with different components. These resins are used in wood production, molding materials, surface coatings, textile, leather, rubber, and cement industries. It is also used in producing other chemicals. This thesis deals with particularly phenol-formaldehyde (PF) and lignin-phenol-formaldehyde (LPF) resin in the plywood industry. Formaldehyde is also formed naturally in troposphere from methane and occurs everywhere around us. It is to be known that formaldehyde emissions (FE) have an impact on people's health when exposed to large amounts. According to International Agency for Research on Cancer (IARC), the gas is a carcinogen to humans. (IARC, 2006, 45, 48, 94)

In this bachelor's thesis, formaldehyde emissions in plywood panels are observed by two determination methods which are desiccator (ISO 12460-4:2016) and gas analysis method (ISO 12460-3:2015). The main targets of this research are to find a possible correlation between these two methods, and also to compare FE of PF and LPF resins. Trial points of test samples are picked out precisely and the results are predicted to fluctuate according to the variables. Analyzable parameters are wood species, glue factor, hot press time and resin type. Study also includes error estimation. Thesis consists of theoretical and empirical research. The theoretical part takes a closer look at the determination methods that are examined in this research and observes the variables that may affect the results. In the empirical part of the report, the FE results are analyzed, and the possible correlation coefficient between two determination method is calculated. Also, comparison of LPF and PF takes place in that chapter.

The research is carried out with UPM Biochemicals, which is part of UPM-Kymmene Oyj - corporation. UPM is an employer of 18,400 people in a total of 46 countries. In 2019, total sales of UPM were 10,2 billion euros. The company is determined to strive towards carbon neutrality and managed to reduce CO<sub>2</sub> emissions by 6 % compared to the last year. UPM Biochemicals produce sustainable and innovative solutions in the field of wood-based biochemicals. The possible fields of use are bottles, textiles, packaging, composites, resins, de-icing products, and functional fillers. (UPM-Kymmene Oyj, 2019, 10, 55, 138)

## **2 PLYWOOD PANELS AND RESINS**

### **2.1 Plywood**

Plywood panel is a rigid flat sheet made from wood by thin layers of veneer glued together. Veneers are glued with grain facing 90 degrees to the previous one, providing a strong final product. Veneers can be made from various kinds of trees. The final product itself can be a mixture of several types of veneer (combi) or one tree panel. UPM makes most of their veneers from birch and spruce. (WisaPlywood) In this study, birch and spruce panels are studied. Plywood panels have various end use possibilities as it is a strong and ecological construction material. The most common use for plywood panels is in construction, as it can be exploited widely from building's framework to interior.

The manufacture of plywood starts with cutting the trees into shorter logs. Logs are then turned, getting one long piece of thin veneer. The veneer is cut into pieces either before or after the drying, this varies depending on the production line. After the veneer is dried and cut, it is time to sort different qualities from one another. Sorting is important because some of these veneers are too narrow or have holes in them. To save the material, this kind of pieces are filled and jointed. After refining, the veneers are ready to be glued and pressed. Application of the adhesive can be done by few different methods – with roller, curtain, foam extruder or spray coater. In the finishing part of the production line takes place sawing, sanding, grading, and packaging. (Koponen, 2002, 28, 67)


### **2.2 Phenol-formaldehyde resin**

Resins are used in plywood manufacturing to make adhesive, the most common ones in the field are phenol-formaldehyde (PF) and urea-formaldehyde (UF) resins. In this thesis, only the former is studied. Adhesive consists of hardener, water, and resin, and is formed in the mill site, according to the tailored recipe for each factory. The adhesive is ready for operation when the viscosity reaches the desired value. (Varis, 2019, 81-82) Resin plays an important role on the final product's quality, as gluing of the veneers is one of the most crucial phases of the manufacturing (Koponen, 2002, 65).

Formation of PF resin happens with phenol and formaldehyde condensation, which is stopped halfway through the reaction. By adding alkaline catalyst, such as sodium hydroxide (NaOH), makes the product resol-type (Pizzi, 1983, 144). The condensation reaction of the resin is completed in the phase of hot pressuring, reaching the perfect hardening of the seam joint. PF resin-based adhesive's recipe has remained almost the same since the 1950's as it suits well for exterior use. (Varis, 2019, 135, 236)

### 2.3 Lignin

Lignin (figure 1) is a polymer, which is the second most abundant renewable resource after cellulose. It is one of the main components of plants, naturally occurring everywhere around us. In the branch of industry, it is possible to collect huge amounts of this nature's product as it is a by-product in papermaking and bioethanol process. Lignin is the second major building material of wood with the composition ranging between 20 % - 30 %. Extraction of lignin is possible to be done under different circumstances affecting the features of the lignin and therefore the process of crosslinking to PF resin. (Pizzi, 1989, 155; Mancera et al., 2011, 2072; Alén, 2011, 33) This by-product is estimated to have a production capacity up to 50 tons per year, but 98 % of this lignin is utilized for energy (Kun and Pukanszky, 2017, 618).



**Figure 1.** Chemical structure of one major monolignol (Hatfield and Vermerris, 2001).


Chemical modification of lignin is required as it is impossible to extract lignin from plants without one. The separation is done during another chemical process and lignin is usually just a by-product of the original process. Lignin extraction is possible to be carried out for example with soda, kraft, sulfite, organosolv process or steam explosion. In this thesis, only the kraft process is being observed as it is one of the commonly used pulping methods. The conventional kraft pulping is executed with sodium hydroxide (NaOH) and sodium sulfide (Na<sub>2</sub>S). The cooking fluid is called white liquor and it assists the lignin to degrade. Outcome

of the cooking is called black liquor and its dry mass contains 25 % to 31 % of lignin depending on the wood. (Kun and Pukanszky, 2017, 620-622; Alén, 2011, 76, 98) To reach a higher efficiency of the pulp mill, technology called LignoBoost can be utilized. Providing pure lignin with low ash content is done by evaporating black liquor and then lowering the lignin's pH with carbon dioxide (CO<sub>2</sub>). Precipitated lignin is dewatered and then mixed with acidified water. For the slurry mixture to become so called lignin cakes, the slur is once again dewatered. (Valmet, n.d.)

#### **2.4 Lignin-phenol-formaldehyde resin**

Research in alternative adhesives has been done all over the world for quite a long time. In Finland for example, lignin-based adhesive called Karatex, was started to be made in the 1970's. Due to the low prices and rapid development of phenol-based resins, the lignin-based resin was prevented from large spread to the markets. (Varis, 2019, 135) The development and generalization of this kind of alternative is now more essential than ever. By replacing even some share of the phenol with lignin in resins, less fossil raw materials are consumed.

The environmental and economic aspects of this waste product make the raw material engaging. Native lignin (figure 1) is detected to have a similar structure as PF resins (figure 2). Cross-linking of LPF however requires longer pressing time and higher temperatures as to PF resins. (Pizzi, 1983, 254) These requirements and the modification of lignin reduces the effectiveness and increases the cost of this process. Due to low reactivity of lignin, increasing the lignin content above 30 % was not feasible for a long time. UPM is determined for heading towards bigger substitution rates and in 2013, UPM-Kymmene Corporation applied for a patent to increase the reactivity of lignin. The invention showed that by treating lignin with alkalation, it is possible to reach a significantly higher substitution of phenol. This was a major step towards the goal as higher content of lignin have been successful since. (Pietarinen et al., 2014, 1)

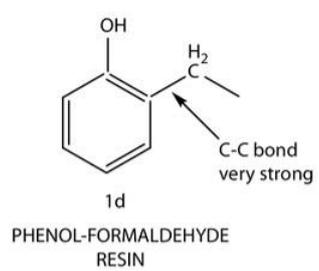


**Figure 2.** The chemical structure of PF resin (Kumar and Pizzi, 2019).

### 3 FORMALDEHYDE EMISSIONS

#### 3.1 Formaldehyde

Formaldehyde (figure 3) is produced from methanol or methane by oxidation in the presence of a catalyst. The source for methanol is natural gas. Formaldehyde is widely studied and therefore is one of the best-known pollutants for indoor air. (Salthammer et al., 2010, 2537-2538) The compound is mainly used in producing resin with different components. These resins are used in wood production, molding materials, surface coatings, textile, leather, rubber, and cement industries. It is also a feedstock for producing other chemicals. (IARC, 2006, 45) In this study, only phenol-formaldehyde (PF) and lignin-phenol-formaldehyde (LPF) combinations in plywood production are being observed.



**Figure 3.** The chemical structure of formaldehyde (Kumar and Pizzi, 2019).

Formaldehyde is a natural compound as plants naturally contain formaldehyde, so the exposure outdoors is inevitable. The concentrations in the outdoor air differ greatly depending on the region. The value in the northern and central Europe, as well the United States, lies between 5 to 15 parts per billion (ppb) as to the cities with high photochemical air pollution has the average value between 20 to 30 ppb. Outdoor levels are however lower than indoor measures caused by the low air exchange indoors. The indoor emissions are difficult to define as there are so many factors affecting, but according to Salthammer (2013) the levels are roughly around 40 ppb. There are many potential sources for formaldehyde release indoor, for example, wood-based products, insulation, and coating materials. Also, combustion releases formaldehyde, which is a strong source in wood-heated homes. (Salthammer, 2013, 3323-3324; Salthammer et al. 2010, 2541-2542)

### 3.2 Guidelining the emissions

According to IARC, formaldehyde is a carcinogen to humans (IARC, 2006, 45). This has led to new regulations holding considerably lower exposure limits, in both workplace and nonoccupational environment. Nonoccupational limits are in general lower than the workplace ones. There are few ways for guidelining the formaldehyde emissions. One of the ways is by category, when health authorities establish exposure levels. The most common guideline used is by the World Health Organization (WHO). WHO has established a recommendation limit of  $0,1 \text{ mg/m}^3$  (80 ppb) to short-term exposure indoors (WHO, 2010, 142). The second possible way for setting guideline values is by region. (Salthammer et al., 2010, 2551)

Material testing methods for formaldehyde emissions can be divided into two groups by determining the content or the release from the panel (Salthammer et al., 2010, 2549). In this study we are only observing gas analysis and desiccator method, which are introduced in the next chapter more closely. Both of these methods measure the actual formaldehyde releasing from the panel. According to the European standard EN 636, the interior panels must have a classification of E1 or E2. The exterior panels may not be classified. However, the approved methods for this classification are EN 717-1 (chamber method) and EN 717-2 (gas analysis). As desiccator method is not admitted for guidelining the plywood FE in Europe, the aim of this thesis is to find correlation between gas analysis and desiccator method. The correlation value would help predicting the FE from gas analysis method.

Standards for both limit values and measure methods are presented in table 1. The limits for formaldehyde release for wood-based panels by gas analysis determination are presented in EN 13986 standard. This European standard represents the panels used in construction. Classification is executed between two categories of E1 and E2. The Japanese Industry Standard JIS A 5908 gives limit values for panels determined by desiccator method. The possible classes are from one to four stars, four being the lowest release amount. According to Marutzky and Dix (2004), the Japanese F\*\* is most equivalent to European class of E1 (cited in Salem, 2011). The relationship of these limit values are shown in the table 2 below. (Salem, 2011, 7-8, 81) Formaldehyde emissions of UPM plywood panels are however significantly below the guidelines (Seppänen, 2019).

**Table 1.** Standards and methods studied in this thesis.

<b>Standard for limit values</b>	<b>Determination method</b>
EN 13986	EN 717-2, ISO 12460-3
JIS A 5908	JIS A 1460, ISO 12460-4

**Table 2.** FE limit values for plywood in EN 13986 (gas analysis) and JIS A 5908 & 5905 (desiccator method).

	<b>Gas analysis</b> [mg/m <sup>2</sup> h]	<b>Desiccator</b> [mg/L]	
		≤ 0,3	<b>F*****</b>
		≤ 0,5	<b>F****</b>
<b>E1</b>	≤ 3,5	≤ 1,5	<b>F**</b>
<b>E2</b>	≤ 8		

### 3.3 Methods for reducing the emissions

Even if the formaldehyde emissions today were below the guidelines, the regulations are constantly tightening. Also, the environmental awareness and the concern for people's health demand actions for decreasing the emissions in the future. Formaldehyde is possible to be determined in different phases of adhesive's life cycle. The same goes with the emission reduction, as it is possible to concentrate on board production or on the subsequent emissions. In this thesis, the service life emissions are observed more closely. The methods studied for reducing FE are alternative adhesive, pressing time and glue factor. Also, the factor of wood species is discussed.

One of the factors affecting the FE is the species of wood. As mentioned above, plywood can be made of various kind of wood. In this thesis, we are only observing birch and spruce

veneers. Weigl et al. (2009) declare that in general, hardwood species contain less formaldehyde than softwoods. The supposition is, that veneers made of birch emit less formaldehyde than veneers made of spruce. According to Böhm et al. (2012), emission values of birch truly are lower than spruce's ones – the exact values from the study are presented in table 3.

**Table 3.** FE values measured with gas analysis from solid wood.

<b>Wood species</b>	<b>FE values [mg/m<sup>2</sup>h]</b>
Birch	0,049
Spruce	0,069

There are few known parameters affecting the emission rate that can be adjusted in the board production process. These adjustments are known to affect the FE during production, but not all the modifications have an impact on the subsequent emissions. During the press cycle, high moisture content slows the glue joint hardening reaction and causes more evaporation, which in turn increases the release of formaldehyde. According to Carlson et al. (cited in Johansson et al., 2002), the formaldehyde emissions increase with a longer pressing time and higher pressing temperature. The role of the glue factor is controversial. From one standpoint, more adhesive stands for higher emissions, but at the same time it can provide a tighter structure of the panel. Higher density in turn tends to keep the emissions confined and reduces the FE during production, but also in service life. This issue will be examined in the results chapter. (Johansson et al., 2002, 161; Chan Bao and Feng Hu, 2012, 97)

Reduction in both formaldehyde and greenhouse gas (GHG) emissions are possible to achieve by alternative adhesives. Formaldehyde used in resins today is manufactured via synthetic gas. Production of formaldehyde might however be done utilizing biomethane, which could be both economic and ecological option compared to traditional one (Singh, Devnani and Pal, 2016, 467). Alternative adhesives can be made by replacing traditional components by polyisocyanates or natural resources, such as tannin, lignin or vegetable proteins (Chan Bao and Feng Hu, 2012, 98-99). In this thesis, only lignin-based alternative is

studied. Alternative adhesives offer a broad platform for research to move towards more sustainable wood-based panel (WBP) production in the future.

One method for decreasing the subsequent formaldehyde release is post-treating the panels, for example by coating or sealing the edges. However, in this case, other volatile organic compound (VOC) emissions should be taken into consideration. (Chan Bao and Feng Hu, 2012, 98-99) Under consideration should also be the other possible impacts of these modifications. Using these alternative compounds do not make the product yet biodegradable and the disposal remains challenging. The manufacturing of these panels should be economically sensible, and all the alternatives mentioned above are today not as competitive in terms of production as the chemicals currently used. Harnessing these alternatives for industrial use demand resources.

## 4 DETERMINATION METHODS

Determination methods that are studied in this thesis are desiccator (ISO 12460-3:2015) and gas analysis method (ISO 12460-4:2016). Both methods test the actual formaldehyde release from the panel by measuring the quantity of emitted formaldehyde absorbed in water. The major practical differences between these methods are the time required for the determination and the cost of the equipment. Both determinations are carried out in duplicate, and if differences in the average results over 20 % occur, also third tests should be carried out. In this chapter, both methods are studied more closely.

### 4.1 Gas analysis method

The European standard ISO 12460-3 represents the method of gas analysis, also referred as EN 717-2. Determination of formaldehyde with gas analysis method is taken place in a closed chamber with air temperature of  $(60 \pm 0,5)$  °C and relative humidity of  $\leq 3$  %. Throughout the testing, the chamber is to maintain an overpressure of  $(1100 \pm 100)$  Pa. The chamber's airflow of  $(60 \pm 3)$  L/h is led from the chamber into paired wash bottles (figure 4). The air contains the formaldehyde from the test pieces. FE from test pieces is measured for 4 hours. A new series of wash bottles are replaced with the old ones every hour. The actual content of the formaldehyde is determined photometrically. Content of the formaldehyde is given in  $\text{mg}/\text{m}^2\text{h}$ .



**Figure 4.** Wash bottles of gas analysis method (Kumar and Pizzi, 2019).

In gas analysis method, test piece dimensions are  $(400 \pm 1) \text{ mm} \times (50 \pm 1) \text{ mm} \times$  board thickness. Three test pieces for this determination is needed. The edges of the test piece must be sealed, and the unsealed area shall be calculated. The board thickness does not have an impact on the emitting surface area as the edges are sealed. The target for total emitting surface area is  $0,04 \text{ m}^2$ . Example calculation for the surface area is shown down below (equation 1).

$$A = l_x * l_y * 2 \quad (1)$$

$$A = (400 \text{ mm} * 50 \text{ mm}) * 2$$

$$A = 40000 \text{ mm}^2 = 0,04 \text{ m}^2$$

Gas analysis method today has a new standard (ISO 12460-3:2020), but in this thesis, the determination was executed by the norms of the old one because of the timeframe. The biggest adjustment in the new standard was test period changing from 4 hours to 3 hours, which makes the method even faster to execute. Despite the fact that the duration of this measurement is short, this method requires a great investment in equipment. This can be considered as a disadvantage of this method.

## 4.2 Desiccator method

The second determination method studied is desiccator method, which is represented in the European standard ISO 12460-4. The absorption of formaldehyde is carried out with  $(300 \pm 1) \text{ ml}$  of water at  $(20 \pm 1) \text{ }^\circ\text{C}$ . The water dish is placed at the bottom of the desiccator and the test pieces on a wire mesh above the dish (figure 5). Emissions are kept confined for  $24 \text{ h} \pm 10 \text{ min}$  in the desiccator. However, before the actual testing, test pieces should be conditioned for 7 days. This is considered as a disadvantage of this determination method. This passive testing method do not require high-cost investments and is therefore more feasible. As in gas analysis method, the actual content of the formaldehyde is determined photometrically. Content of the formaldehyde is given in  $\text{mg/L}$ .



**Figure 5.** Desiccator method (Kumar and Pizzi, 2019).

In desiccator method, the test piece dimensions are  $(150 \pm 1) \text{ mm} \times (50 \pm 1) \text{ mm} \times$  board thickness. The target for total emitting surface area is  $0,18 \text{ m}^2$ . The number of the test pieces depend on the surface emitting area of one individual piece. By increasing the amount of test samples, it might be possible to reach a closer value for target emitting area. Example calculation for the surface area is shown down below (equation 2). The calculation represents 5-ply spruce plywood with board thickness of 15 mm (appendix I). The dimensions of these particular test piece are therefore  $150 \text{ mm} \times 50 \text{ mm} \times 15 \text{ mm}$ .

$$A = (l_x * l_y + l_x * l_z + l_y * l_z) * 2 \quad (2)$$

$$A = (150 \text{ mm} * 50 \text{ mm} + 150 \text{ mm} * 15 \text{ mm} + 50 \text{ mm} * 15 \text{ mm}) * 2$$

$$A = 21000 \text{ mm}^2 = 0,021 \text{ m}^2$$

The emitting surface area of one test piece differs greatly from the target value. The total amount of required test pieces is calculated down below (equation 3). The final emitting surface area is achieved by multiplying the individual value by the amount of the test pieces.

$$x * A = 0,18 \text{ m}^2 \quad (3)$$

$$x = \frac{0,18 \text{ m}^2}{0,021 \text{ m}^2} = 8,57 \approx 9$$

## 5 ANALYZING METHODS AND ERROR ESTIMATION

### 5.1 Correlation between methods

One of the main targets of this thesis is to find a correlation coefficient for formaldehyde emissions determined by gas analysis and desiccator method. This is done by utilizing the results from the test pieces. The correlation between determination methods is studied through linear correlation. Correlation value of at least 0,7 is considered as a strong correlation (Ratner, 2009). Correlation coefficient is first looked at as an overall review. As presented in table 3, wood species tend to have an impact on the formaldehyde emissions itself. For this reason, correlation value is also calculated with birch and spruce separately. Based on wood species observation, it is possible to tentatively infer, does this parameter affect the FE from the panel and is the correlation more reliable individually.

### 5.2 Adjustments for FE reduction

The hypothesis for adjustments to reduce formaldehyde emissions (table 4) are gathered from various literature. The assumptions are confirmed or repealed by analyzing the test results in the next chapter. The results are studied separately by both methods. Glue factor and pressing time are analyzed through linear correlation. Wood species and adhesive parameter are observed generally.

**Table 4.** Hypothesis for FE reduction.

<b>Parameter</b>	<b>Adjustment for reduction of FE</b>
Glue factor	Less adhesive
Wood	Hardwood over softwood
Pressing time	Longer pressing time
Adhesive	Lower molar ratio (less formaldehyde)

One of the main targets of this thesis is to compare the FE from the plywood panels made with PF and LPF resins. This is done by visual observation of bar charts. From table 4 it is

possible to infer that with smaller molar ratio, the release of formaldehyde is also lower. The amount of formaldehyde in the resin varies by recipe. The comparison between LPF and PF is done to see, is there any correlation between the amount of lignin in the resin and formaldehyde emissions (molar ratio).

### 5.3 Error estimation

Error in measuring process can be caused either experimental or observational aspects. Observational error in turn can be divided into systematical error and random error. In this thesis, only random error is considered. Random error is unpredictable and impossible to eliminate from the measurement. It is caused by the environmental conditions and measuring instruments. Random error is calculated for both of the methods separately.

Calculations for random error in determination methods are done by using the formaldehyde release results from the panel, which includes the background concentration. The percentage spread of the result is calculated using spread and the mean of the measurement results. This in turn is used calculating the actual random error. Example calculation for random error in gas analysis method is presented down below (equation 4).

$$d_{ri}(\%) = \frac{d_i}{\bar{x}} * 100 \quad (4)$$

$$s_{ri}(\%) = \sqrt{\frac{\sum [d_{ri}(\%)^2]}{2 * n}}$$

$$s_{ri}(\%) = \sqrt{\frac{3165,14 \%}{2 * 42}} = 6,14 \%$$

Gaussian normal is used to calculate the expanded uncertainty. With the confidence level of 95 %, the coverage factor  $k$  is 2. The calculation for expanded uncertainty of 95 % for gas analysis method is shown down below (equation 5).

$$U = k * s_{ri} \quad (5)$$

$$U = 2 * 6,14 \% \approx \pm 12 \%$$

Equations 4 and 5 are widely used in estimating the error in measuring in general. More precise calculations are shown in appendix II for gas analysis method and in appendix III for desiccator method. All results for error estimation are presented in table 5.

**Table 5.** Random error and expanded uncertainty for both determination methods.

	<b>Gas analysis method</b>	<b>Desiccator method</b>
<b>Sri</b>	6,14 %	17,78 %
<b>U</b>	12 %	36 %


The uncertainty of desiccator method is significantly higher than the gas analysis one. This can be taken under consideration in the results chapter when comparing the FE levels. Error estimation supports in assessing the reliability of the results and making conclusions.

## 6 RESULTS


There were total of 42 test pieces for both determination, which are analyzed in this chapter. Both measurements were carried out in duplicates. Measurements were performed by UPM-Kymmene Oyj. More specific description of the samples is to be found in appendix I. In the chapter 6.1, correlation coefficient is calculated for testing methods. Parameters affecting the formaldehyde emissions are studied in the chapter 6.2. Analyzable parameters are wood species, glue factor, pressing time and resin type. Formaldehyde emissions of LPF and PF resins are compared in the same chapter.

### 6.1 Comparing testing methods

All the results from both determination methods are presented in figure 6. This gives an overview from the correlation between methods. As can be tentatively seen from the figure 6, there is no clear correlation between methods. The drop in emissions at the end of the graph is caused by the wood species changing from spruce to birch. More precise observation is seen in figure 7.

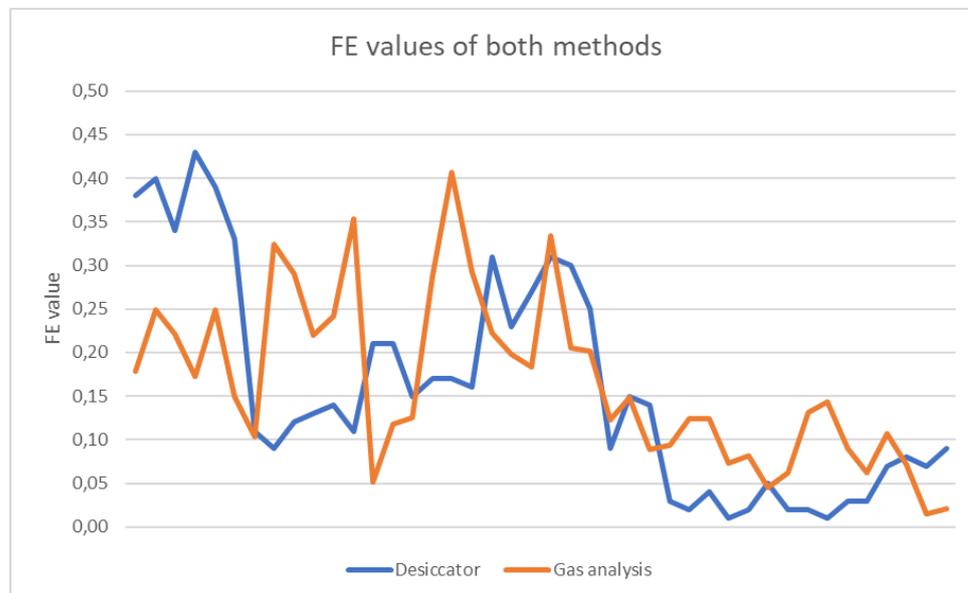


**Figure 6.** FE values of both methods.

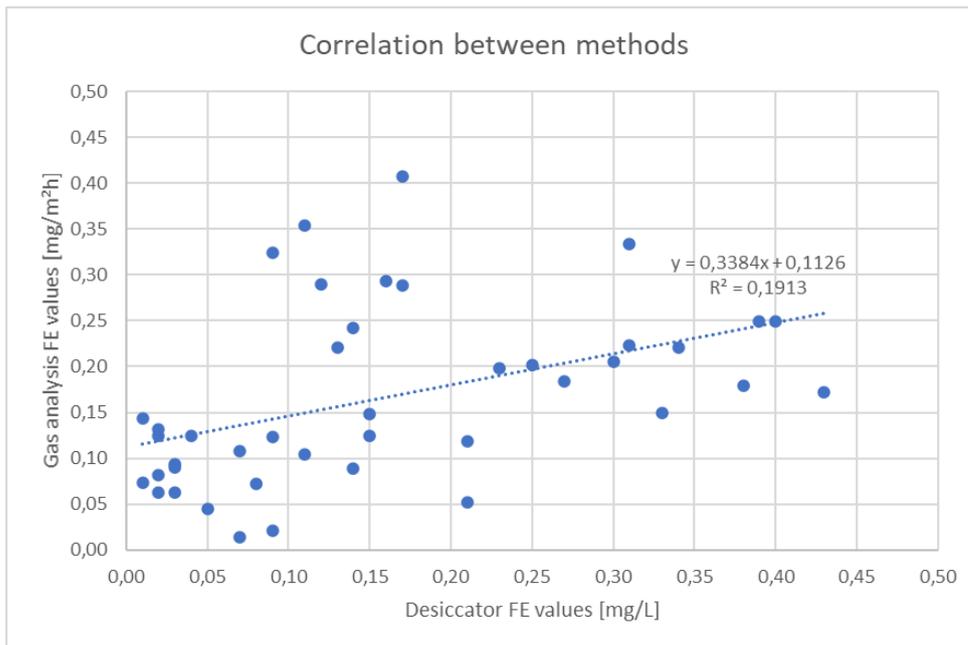


**Figure 7.** Correlation between determination methods.

Wood species is estimated to have an impact on the FE (table 3) and therefore both wood species are studied also individually (figure 8 and figure 9). As seen in table 6, the correlation with both wood species is significantly better than the correlation individually. A closer observation with certain variable gives a more decent outcome. This means, that in this case, study based on wood species is more reliable. The difference in the magnitude and the sign of the slope between overall and individual results cause contradiction. It is possible to infer that wood species in the same chart manipulate the results. It is also confirmed that the wood species have an impact on the FE from plywood panels.

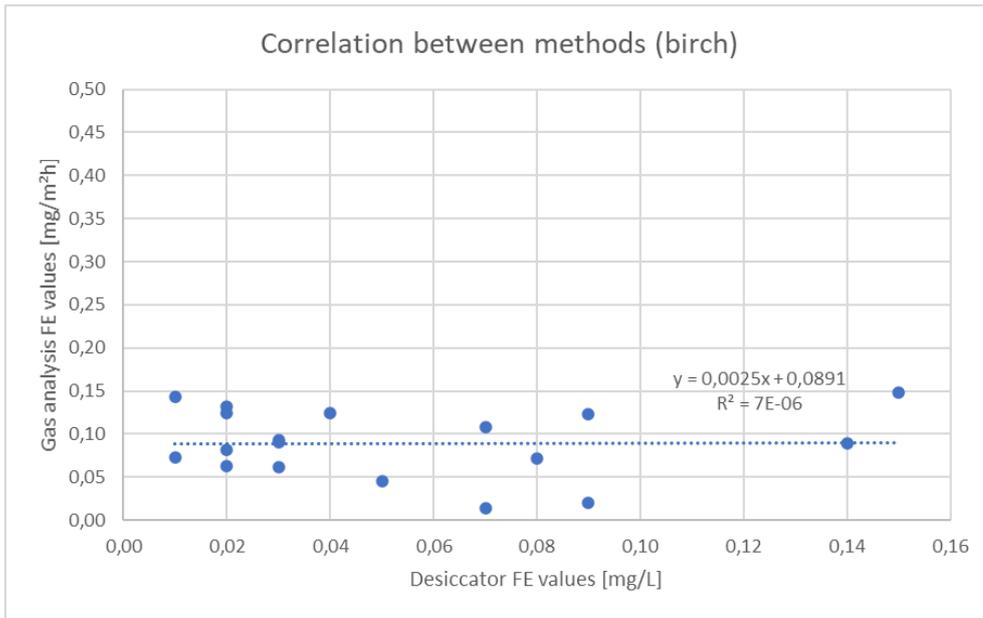

**Figure 8.** Correlation between determination methods for birch plywood.

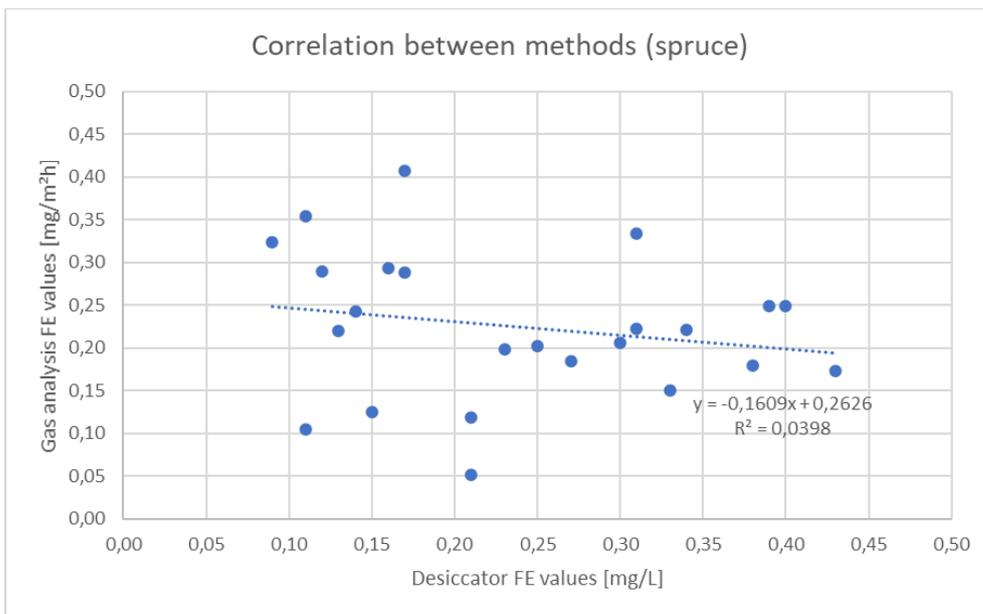

**Figure 9.** Correlation between determination methods for spruce plywood.

**Table 6.** Correlation coefficient ( $R^2$ ) between determination methods.

<b>Birch and spruce</b>	0,1913
<b>Birch</b>	$7 \cdot 10^{-6}$
<b>Spruce</b>	0,0398

## 6.2 Comparing the emissions of PF and LPF resins

Tables 7-9 present the results from appendix IV and appendix V. As noticed, the overall results including both wood species have a higher correlation coefficient with every variable than the individual ones. In this study, only the pressing time correlation with desiccator method gives a result for strong correlation. However, this scenario was already presented in the chapter 6.1, where conclusion of wood species manipulating each other was also drawn. For these reasons, this correlation is not considered as a relevant correlation.

By taking tables 8 and 9 under a closer investigation, it is possible to see that no reliable correlation is detected between the value of formaldehyde emissions and glue factor or pressing time. Only plywood made out of spruce reaches a pressing time correlation of 0,6833 measured by desiccator method (table 9), which is the closest to the limit value of 0,7. However, the correlation with gas analysis in the same situation is only 0,0687 (table 9). If the actual correlation would exist, the gas analysis value would also be significantly higher. Also, the expanded uncertainty of gas analysis is much smaller than the desiccator method one, which makes the former method more reliable and confirms the result of no correlation being available.

**Table 7.** Correlation coefficient ( $R^2$ ) of glue factor and pressing time.

	<b>Gas analysis method</b>	<b>Desiccator method</b>
Birch and spruce		
<b>Glue factor</b>	0,2386	0,1991
<b>Pressing time</b>	0,3851	0,7385

**Table 8.** Correlation coefficient ( $R^2$ ) of glue factor and pressing time (birch).

Birch	Gas analysis method	Desiccator method
<b>Glue factor</b>	0,0942	0,0270
<b>Pressing time</b>	0,0026	0,0795

**Table 9.** Correlation coefficient ( $R^2$ ) of glue factor and pressing time (spruce).


Spruce	Gas analysis method	Desiccator method
<b>Glue factor</b>	0,0039	0,1042
<b>Pressing time</b>	0,0687	0,6833

As proven that neither the glue factor nor the pressing time has a predictable impact on the formaldehyde emissions, gives the opportunity to compare the test results as an average value. This also makes the outcome more trustworthy as there are more measuring points available to compare. Resin 1-3 represent plywood panels made out of birch while resin 4 and 5 are recipes for spruce panels. Resins 1, 2 and 4 are lignin-based resins. This information about resins is gathered in table 10 down below.


**Table 10.** Wood species and types of resin.

	Wood species	Resin type
<b>Resin 1</b>	Birch	LPF
<b>Resin 2</b>	Birch	LPF
<b>Resin 3</b>	Birch	PF
<b>Resin 4</b>	Spruce	LPF
<b>Resin 5</b>	Spruce	PF

As is seen from figures 10 and 11, spruce tends to have a higher level of emissions with both determination methods. With great expanded uncertainty of desiccator method, the FE of spruce panels might reach remarkably higher than the emissions of birch panels. The differences in emissions can be explained by the natural wood consistence of formaldehyde (table 3). This in turn confirms the assumption of the influence of wood species once again.

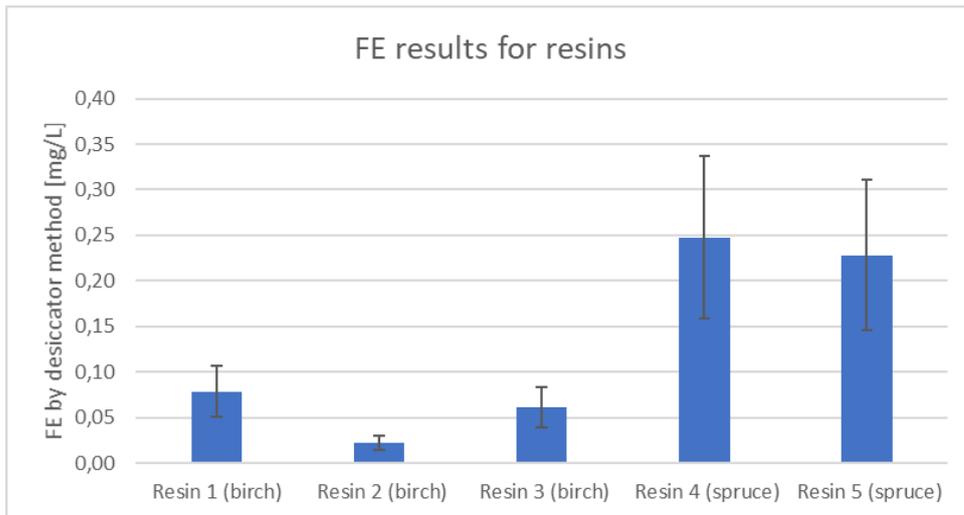

**Figure 10.** FE results for different resin types, desiccator method.

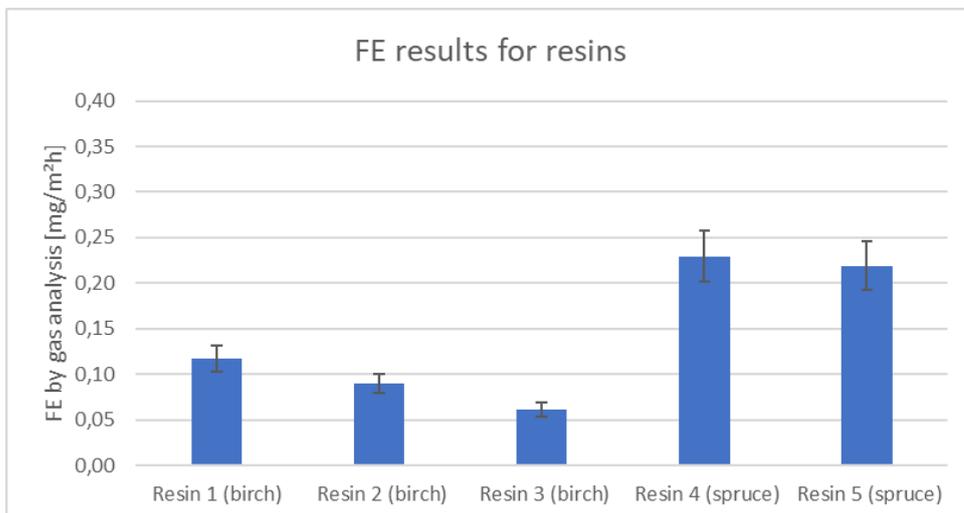

**Figure 11.** FE results for different resin types, gas analysis.

With smaller molar ratio, also the FE is estimated to be lower. The actual data for molar ratio is however not presented in this study, and the review concentrates on the relationship between FE and lignin. Focusing only on the birch panels, it is seen that resin 1 and 2 (which

are lignin-based), do not differ considerably from resin 3 (which is phenol-based). In fact, with gas analysis method, PF resin actually has the lowest FE value of all the results. The same can be said with spruce panels. Resin 4 (lignin-based) really has a higher FE value than resin 5 (phenol-based) with both determination methods. It can be inferred that FE is independent from the amount of lignin in the resin.

## 7 CONCLUSIONS

One of the main targets of this thesis was to find a correlation coefficient for gas analysis and desiccator method. These methods measure the level of formaldehyde emissions from plywood panels. At this very moment, there is no EN-standard available for desiccator method. Strong correlation coefficient would give a possibility for utilizing this cost-efficient and accessible determination method in Europe. The emissions release could be measured close to the output of the panels and would also reduce the need for extra transport. This in turn would cut the GHG emissions.

Possible correlation coefficient would have assured the need and also the possibility of EN-standard for desiccator method. In this thesis, only the linear correlation was studied, and no clear correlation was found between these methods. It might be possible to find a correlation coefficient with a more complex equation, but this could be confirmed or repealed only with more research. Another major aspect affecting the current lack for EN-standard is the uncertainty of desiccator method. It was calculated that the expanded uncertainty of gas analysis is 12 % and the value of desiccator method is 36 %, which is remarkably higher compared to the gas analysis one. The lack of correlation and high uncertainty of desiccator method complicates the formation of reliable EN-standard.

Another main target of this bachelor's thesis was the comparison of PF and LPF resin. In order to compare the formaldehyde emission levels of these resins, it was crucial to identify all the other variables affecting the overall emissions. Variables that were considered in this study were wood species, glue factor, pressing time, and resin type. Hypotheses for these variables affecting the FE (table 4) were collected from literature. Only the hypothesis for wood species was confirmed, and all the other variables did not appear to correlate with the emissions. The distinction between hardwood and softwood FE can be explained with the variation of natural consistence. Also, the recipes of the resins have differences and are estimated to have an impact on the release.

With superficial study of the lignin in the resin, no clear relationship between FE and lignin was found. The hypothesis of the study however concerned the molar ratio of the resin, not

the actual amount of lignin. The recipes of resins could be studied more closely to achieve a better review of this relationship. Substitution of phenol still has big environmental impacts, even if the FE levels did not appear to decrease. By utilizing this renewable by-product for resin manufacturing instead for using it as a source of energy, less fossil raw materials are consumed. This in turn reduces the greenhouse gas emissions. GHG emissions can be reduced further by concentrating on the source of formaldehyde in resin. Instead of using traditional formaldehyde, it can also be produced from biomethane.

## 8 SUMMARY

The main targets of this bachelor's thesis were to study the correlation between gas analysis method and desiccator method and to compare LPF and PF formaldehyde emissions. The study was related to plywood manufacturing and was made in cooperation with UPM Biochemicals. The study is needed for predicting the results and for estimating the future actions for reducing the formaldehyde emissions.

In the literature part of the thesis, plywood manufacturing, components of the resin, and determination methods were studied more closely. Also, the standards and legislation related to plywood panels were observed. Hypothesis for the possible reduction of formaldehyde emissions with different parameters were made. The parameters studied in this thesis were wood species, glue factor, pressing time, and resin type. Error estimation for both methods were calculated.

In the result part of the thesis, all measurements were analyzed. Determination methods were compared to one another. The comparison led to a result of no clear correlation existing between gas analysis and desiccator method. Based on the research result, utilizing desiccator method with no EN-standard today is not possible. In the same chapter, hypothesis for different parameters affecting the FE were either confirmed or repealed based on test results. The effect of wood species was confirmed as it was detected that hardwood emits less formaldehyde than softwood. All the other hypotheses were repealed, as they were noticed not to have a clear impact on the FE of the panel.

## REFERENCES

Alén, R. (2011). *Papermaking Science and Technology – Book 20. Biorefining of Forest Resources*. Helsinki: Paper Engineers' Association. 381 p. ISBN 9789525216394

Böhm, M., Salem. M. Z. M. and Srba, J. (2012). *Formaldehyde emission monitoring from a variety of solid wood, plywood, blockboard and flooring products manufactured for building and furnishing material*. *Journal of Hazardous Materials*. [online]. Vol 221-222. p. 68-79 Available at: <https://www.sciencedirect.com/science/article/abs/pii/S0304389412003913?via%3Dihub> [Accessed 10 Feb. 2021]. ISSN 0304-3894

Chan Bao, C. and Feng Hu, L. (2012). *Formaldehyde: Chemistry, applications, and role in polymerization*. [online]. New York: Nova publishers. Available at: <https://lib.sk/book/2577490/203b51?regionChanged=&redirect=233526332> [Accessed 17 Jan. 2021]. 207 p. ISBN 9781622572144

Dunky, M. (1998). *Urea-formaldehyde (UF) adhesive resins for wood*. *International Journal of Adhesion and Adhesives*. [online]. Vol 18. Issue 2. p. 95-107 Available at: <https://www.sciencedirect.com/science/article/abs/pii/S0143749697000547> [Accessed 17 Jan. 2021]. ISSN 0143-7496

Hatfield, R. D. and Vermerris W. (2001). *Lignin formation in plants. The dilemma of linkage specificity*. *Plant Physiology*. [online]. Vol 126. Issue 4. p. 1351-1357 Available at: [https://www.researchgate.net/publication/11843451\\_Lignin\\_Formation\\_in\\_Plants\\_The\\_Dilemma\\_of\\_Linkage\\_Specificity](https://www.researchgate.net/publication/11843451_Lignin_Formation_in_Plants_The_Dilemma_of_Linkage_Specificity) [Accessed 16 Feb. 2021]. ISSN 1532-2548

IARC. (2006). *IARC Monographs on the Evaluation of Carcinogenic Risks to Humans. Volume 88. Formaldehyde, 2-Butoxyethanol and 1-tert-Butoxypropan-2-ol*. [online]. Available at: <https://publications.iarc.fr/106> [Accessed 1 Nov. 2020]. 478 p. ISBN 9283212886

Johansson, C. J., Pizzi, T. and Van Leemput, M. (2002). *Wood Adhesion and Glued Products*. Working group 2: Glued wood products. State of art – report. COST Action E13. [online]. Available at: <http://users.teilar.gr/~mantanis/E13-Glued-Products.pdf> [Accessed 29 Jan. 2021]. 195 p. ISBN 92-894-4892-X

Koponen, H. (2002). *Puutuoteteollisuus 4: Puulevytuotanto*. 3rd ed. Helsinki: Opetushallitus. 201 p. ISBN 9789521314506

Kumar, R. and Pizzi, A. (2019). Adhesives for wood and lignocellulosic materials. [online]. Available at: [https://www.researchgate.net/publication/335603859\\_Adhesives\\_for\\_Wood\\_and\\_Lignocellulosic\\_Materials](https://www.researchgate.net/publication/335603859_Adhesives_for_Wood_and_Lignocellulosic_Materials) [Accessed 16 Feb. 2021]. 516 p. ISBN 9781119605430

Kun, D. and Pukanszky, B. (2017). *Polymer/lignin blends: Interactions, properties, applications*. European Polymer Journal. [online]. Vol 93. p. 618-641 Available at: <https://www.sciencedirect.com/science/article/abs/pii/S0014305716317529> [Accessed 15 Dec. 2020]. ISSN 0014-3057

Mancera, C., Ferrando, F., Salvadó, J. and El Mansouri, N.E. (2011). *Kraft lignin behavior during reaction in alkaline medium*. Biomass and Bioenergy. [online]. Vol 35. Issue 5. p. 2072-2079 Available at: <https://www.sciencedirect.com/science/article/abs/pii/S0961953411000766> [Accessed 15 Dec. 2020]. ISSN 0961-9534

Pietarinen, S., Valkonen S. and Ringena, O. (2014). *Method for increasing the reactivity of lignin*. UPM-Kymmene Corporation. US2014/10259903 B2

Pizzi, A. (1983). *Wood adhesives. Chemistry and Technology*. Vol 1. New York: Marcel Dekker. 384 p. ISBN 9780824715793

Pizzi, A. (1989). *Wood adhesives. Chemistry and Technology*. Vol 2. New York: Marcel Dekker. 432 p. ISBN 9780203733721

Ratner, B. (2009). *The correlation coefficient: Its values range between +1/-1, or do they?* Journal of Targeting, Measurement and Analysis for Marketing. [online]. Vol 17. Issue 2. p. 139-142 Available at: <https://link.springer.com/article/10.1057%2Fjtm.2009.5> [Accessed 8 Mar. 2021]. ISSN 09673237

Salthammer, T., Mentese, S. and Marutzky, R. (2010). *Formaldehyde in the indoor environment*. Chemical Reviews. [online]. Vol 110. Issue 4. p. 2536-2572 Available at: <https://pubs.acs.org/doi/10.1021/cr800399g> [Accessed 17 Jan. 2021]. ISSN 0009-2665

Salthammer, T. (2013). *Formaldehyde in the ambient atmosphere: From an indoor pollutant to an outdoor pollutant?* Angewandte Chemie International Edition. [online]. Vol 52. Issue 12. p. 3320-3327 Available at: <https://onlinelibrary.wiley.com/doi/abs/10.1002/anie.201205984> [Accessed 17 Jan. 2021]. ISSN 1521-3773

Seppänen, I. (2019). Declaration of Formaldehyde. [online]. UPM Plywood Oy. Available at: <https://www.wisaplywood.com/siteassets/documents/certificates/upm-e1-declaration.pdf> [Accessed 29 Jan. 2021].

Singh, D., Devnani, G. L. and Pal. D. (2016). *Biomethane: An efficient source for the production of CNG and formaldehyde*. International Journal of Scientific Engineering and Applied Sciences. [online]. Vol 2. Issue 1. p. 466-470 Available at: [https://www.researchgate.net/publication/290428439\\_Biomethane\\_An\\_Efficient\\_Source\\_for\\_the\\_Production\\_of\\_CNG\\_and\\_Formaldehyde](https://www.researchgate.net/publication/290428439_Biomethane_An_Efficient_Source_for_the_Production_of_CNG_and_Formaldehyde) [Accessed 29. Jan 2021]. ISSN 2395-3470

Suomen standardoimisliitto SFS ry. (2004). *Wood-based panels for use in construction. Characteristics, evaluation of conformity and marking*. SFS-EN 13986 + A1:en. Helsinki: Suomen standardoimisliitto.

Suomen standardoimisliitto SFS ry. (2015). *Plywood. Specifications*. SFS-EN 636 + A1. Helsinki: Suomen standardoimisliitto.

Suomen standardoimisliitto SFS ry. (2015). *Wood-based panels. Determination of formaldehyde release. Part 3: Gas analysis method (ISO 12460-3:2015)*. SFS-EN 12460-3:en. Helsinki: Suomen standardoimisliitto.

Suomen standardoimisliitto SFS ry. (2016). *Wood-based panels. Determination of formaldehyde release. Part 4: Desiccator method (ISO 12460-4:2016)*. SFS-EN ISO 12460-4. Helsinki: Suomen standardoimisliitto.

Remes, M. (2018). Vaneriliiman uusi aikakausi. [online]. UPM-Kymmene Oyj. Available at: <https://www.upm.com/fi/ajankohtaista/artikkelit/2018/01/vaneriliiman-uusi-aikakausi/> [Accessed 29 Jan. 2021].

UPM-Kymmene Oyj. (2019). *Vuosikertomus 2019*. [online]. Available at: <https://ml-eu.globenewswire.com/Resource/Download/d874fbc0-0565-47a9-bac5-47943fe6be9d> [Accessed 11 Nov. 2020].

Valmet. (n.d.). *LignoBoost process*. [online]. Available at: <https://www.valmet.com/pulp/other-value-adding-processes/lignin-separation/lignoboost-process/> [Accessed 14 Jan. 2021].

Varis, R. (2019). *Puulevyteollisuus*. Porvoo: Kirjakaari Oy. 285 p. ISBN 9789526862736

WisaPlywood. *About Plywood*. [online]. Available at: <https://www.wisaplywood.com/products/about-plywood> [Accessed 18 Nov. 2020].

Weigl, M., Wimmer, R. and Sykacek, E. (2009). *Wood-borne formaldehyde varying with species, wood grade, and cambial age*. Forest Product Journal. [online]. Vol 59. p. 88-92 Available at: [https://www.researchgate.net/publication/235664413\\_Wood-borne\\_formaldehyde\\_varying\\_with\\_species\\_wood\\_grade\\_and\\_cambial\\_age](https://www.researchgate.net/publication/235664413_Wood-borne_formaldehyde_varying_with_species_wood_grade_and_cambial_age) [Accessed 9 Feb. 2021]. ISSN 0015-7473

World Health Organization. (2010). *WHO guidelines for indoor air quality: selected pollutants*. [online]. Available at: [https://www.euro.who.int/data/assets/pdf\\_file/0009/128169/e94535.pdf](https://www.euro.who.int/data/assets/pdf_file/0009/128169/e94535.pdf) [Accessed 18 Jan. 2021]. 454 p. ISBN 9789289002134

## APPENDICES

Table 1. Description of the test pieces.


Adhesive	Structure	Glue factor [g/m <sup>2</sup> ]	Pressing time [min]	Des. Gas		
				Formaldehyde emission		
Resin 1	Birch 1,5 mm (9-ply, 12 mm)	145	8	0,090	0,123	
	Birch 1,5 mm (9-ply, 12 mm)	163	8	0,150	0,148	
	Birch 1,5 mm (9-ply, 12 mm)	154	8	0,140	0,089	
	Birch 1,5 mm (9-ply, 12 mm)	145	9	0,030	0,094	
	Birch 1,5 mm (9-ply, 12 mm)	154	9	0,020	0,124	
	Birch 1,5 mm (9-ply, 12 mm)	163	9	0,040	0,124	
Resin 2	Birch 1,5 mm (9-ply, 12 mm)	145	8	0,010	0,073	
	Birch 1,5 mm (9-ply, 12 mm)	163	8	0,020	0,082	
	Birch 1,5 mm (9-ply, 12 mm)	154	8	0,050	0,045	
	Birch 1,5 mm (9-ply, 12 mm)	145	9	0,020	0,062	
	Birch 1,5 mm (9-ply, 12 mm)	163	9	0,020	0,132	
	Birch 1,5 mm (9-ply, 12 mm)	154	9	0,010	0,143	
Resin 3	Birch 1,5 mm (9-ply, 12 mm)	154	8	0,030	0,090	
	Birch 1,5 mm (9-ply, 12 mm)	145	8	0,030	0,062	
	Birch 1,5 mm (9-ply, 12 mm)	163	8	0,070	0,108	
	Birch 1,5 mm (9-ply, 12 mm)	154	9	0,080	0,072	
	Birch 1,5 mm (9-ply, 12 mm)	163	9	0,070	0,015	
	Birch 1,5 mm (9-ply, 12 mm)	145	9	0,090	0,021	
Resin 4	Spruce 3,2 mm (5-ply, 15 mm)	128	6,5	0,380	0,179	
	Spruce 3,2 mm (5-ply, 15 mm)	138	6,5	0,400	0,249	
	Spruce 3,2 mm (5-ply, 15 mm)	148	6,5	0,340	0,221	
	Spruce 3,2 mm (5-ply, 15 mm)	128	7,5	0,430	0,172	
	Spruce 3,2 mm (5-ply, 15 mm)	138	7,5	0,390	0,249	
	Spruce 3,2 mm (5-ply, 15 mm)	148	7,5	0,330	0,150	
	Spruce 2,6 mm (7-ply, 18 mm)	118	8	0,110	0,104	
	Spruce 2,6 mm (7-ply, 18 mm)	128	8	0,090	0,324	
	Spruce 2,6 mm (7-ply, 18 mm)	138	8	0,120	0,290	
	Spruce 2,6 mm (7-ply, 18 mm)	118	9	0,130	0,220	
	Spruce 2,6 mm (7-ply, 18 mm)	128	9	0,140	0,242	
	Spruce 2,6 mm (7-ply, 18 mm)	138	9	0,110	0,354	
	Resin 5	Spruce 2,6 mm (7-ply, 18 mm)	118	8	0,210	0,051
		Spruce 2,6 mm (7-ply, 18 mm)	128	8	0,210	0,118
Spruce 2,6 mm (7-ply, 18 mm)		138	8	0,150	0,125	
Spruce 2,6 mm (7-ply, 18 mm)		118	9	0,170	0,288	
Spruce 2,6 mm (7-ply, 18 mm)		128	9	0,170	0,407	
Spruce 2,6 mm (7-ply, 18 mm)		138	9	0,160	0,293	
Spruce 3,2 mm (5-ply, 15 mm)		128	6,5	0,310	0,223	
Spruce 3,2 mm (5-ply, 15 mm)		138	6,5	0,230	0,198	
Spruce 3,2 mm (5-ply, 15 mm)		148	6,5	0,270	0,184	
Spruce 3,2 mm (5-ply, 15 mm)		128	7,5	0,310	0,334	
Spruce 3,2 mm (5-ply, 15 mm)		138	7,5	0,300	0,206	
Spruce 3,2 mm (5-ply, 15 mm)		148	7,5	0,250	0,202	

**Table 2.** Uncertainty results of gas analysis method.


Measure 1	Measure 2	Average	$d_i$	$d_{ri}(\%)$	$[d_{ri}(\%)]^2$
0,01975	0,01975	0,02	0,000	0,00	0,00
0,03175	0,03325	0,03	-0,002	-4,62	21,30
0,039	0,03975	0,04	-0,001	-1,90	3,63
0,0325	0,02125	0,03	0,011	41,86	1752,30
0,039	0,039	0,04	0,000	0,00	0,00
0,026	0,026	0,03	0,000	0,00	0,00
0,0165	0,0165	0,02	0,000	0,00	0,00
0,05775	0,05775	0,06	0,000	0,00	0,00
0,0525	0,05325	0,05	-0,001	-1,42	2,01
0,0465	0,04725	0,05	-0,001	-1,60	2,56
0,05025	0,0495	0,05	0,001	1,50	2,26
0,053	0,0525	0,05	0,001	0,95	0,90
0,003	0,0025	0,00	0,001	18,18	330,58
0,01975	0,01975	0,02	0,000	0,00	0,00
0,02	0,0205	0,02	-0,001	-2,47	6,10
0,00225	0,00225	0,00	0,000	0,00	0,00
0,021	0,0215	0,02	-0,001	-2,35	5,54
0,036	0,036	0,04	0,000	0,00	0,00
0,02475	0,02475	0,02	0,000	0,00	0,00
0,01275	0,01275	0,01	0,000	0,00	0,00
0,0105	0,0105	0,01	0,000	0,00	0,00
0,0505	0,0505	0,05	0,000	0,00	0,00
0,03025	0,02975	0,03	0,001	1,67	2,78
0,03675	0,03675	0,04	0,000	0,00	0,00
0,02175	0,02175	0,02	0,000	0,00	0,00
0,01575	0,01575	0,02	0,000	0,00	0,00
-0,0045	-0,005	0,00	0,001	-10,53	110,80
-0,004	-0,004	0,00	0,000	0,00	0,00
-0,00375	-0,0045	0,00	0,001	-18,18	330,58
-0,00375	-0,0045	0,00	0,001	-18,18	330,58
-0,0155	-0,015	-0,02	-0,001	3,28	10,75
-0,0135	-0,01275	-0,01	-0,001	5,71	32,65
-0,01675	-0,01675	-0,02	0,000	0,00	0,00
-0,014	-0,014	-0,01	0,000	0,00	0,00
0,022	0,02125	0,02	0,001	3,47	12,03
0,02325	0,024	0,02	-0,001	-3,17	10,08
-0,0125	-0,0125	-0,01	0,000	0,00	0,00
-0,017	-0,017075	-0,02	0,000	-0,44	0,19
0,0115	0,011	0,01	0,001	4,44	19,75
0,006	0,00525	0,01	0,001	13,33	177,78
0,003	0,003	0,00	0,000	0,00	0,00
0,00325	0,00325	0,00	0,000	0,00	0,00
				$\Sigma[d_{ri}(\%)]^2$	<b>3165,14</b>
<b>Random error, <math>S_{ri}(\%)</math></b>					<b>6,14</b>

**Table 3.** Uncertainty results of desiccator method.


Measure 1	Measure 2	Average	$d_i$	$d_{ri}$ (%)	$[d_{ri}(\%)]^2$
0,363	0,375	0,37	-0,012	-3,25	10,58
0,368	0,393	0,38	-0,025	-6,57	43,17
0,323	0,326	0,32	-0,003	-0,92	0,85
0,41	0,397	0,40	0,013	3,22	10,38
0,371	0,38	0,38	-0,009	-2,40	5,74
0,3	0,335	0,32	-0,035	-11,02	121,52
0,114	0,096	0,11	0,018	17,14	293,88
0,086	0,094	0,09	-0,008	-8,89	79,01
0,102	0,135	0,12	-0,033	-27,85	775,52
0,142	0,138	0,14	0,004	2,86	8,16
0,145	0,145	0,15	0,000	0,00	0,00
0,116	0,093	0,10	0,023	22,01	484,42
0,205	0,247	0,23	-0,042	-18,58	345,37
0,229	0,201	0,22	0,028	13,02	169,61
0,18	0,148	0,16	0,032	19,51	380,73
0,171	0,173	0,17	-0,002	-1,16	1,35
0,169	0,16	0,16	0,009	5,47	29,93
0,158	0,162	0,16	-0,004	-2,50	6,25
0,308	0,305	0,31	0,003	0,98	0,96
0,223	0,214	0,22	0,009	4,12	16,97
0,279	0,233	0,26	0,046	17,97	322,88
0,282	0,303	0,29	-0,021	-7,18	51,55
0,28	0,294	0,29	-0,014	-4,88	23,80
0,247	0,233	0,24	0,014	5,83	34,03
0,109	0,09	0,10	0,019	19,10	364,64
0,134	0,18	0,16	-0,046	-29,30	858,45
0,162	0,113	0,14	0,049	35,64	1269,95
0,033	0,033	0,03	0,000	0,00	0,00
0,028	0,02	0,02	0,008	33,33	1111,11
0,034	0,036	0,04	-0,002	-5,71	32,65
0,01	0,013	0,01	-0,003	-26,09	680,53
0,016	0,015	0,02	0,001	6,45	41,62
0,044	0,062	0,05	-0,018	-33,96	1153,44
0,016	0,036	0,03	-0,020	-76,92	5917,16
0,022	0,02	0,02	0,002	9,52	90,70
0,013	0,007	0,01	0,006	60,00	3600,00
0,025	0,032	0,03	-0,007	-24,56	603,26
0,024	0,043	0,03	-0,019	-56,72	3216,75
0,058	0,093	0,08	-0,035	-46,36	2149,03
0,097	0,072	0,08	0,025	29,59	875,32
0,057	0,079	0,07	-0,022	-32,35	1046,71
0,098	0,082	0,09	0,016	17,78	316,05
				$\Sigma[d_{ri}(\%)]^2$	<b>26544,02</b>
<b>Random error</b> $S_{ri}(\%)$					<b>17,78</b>

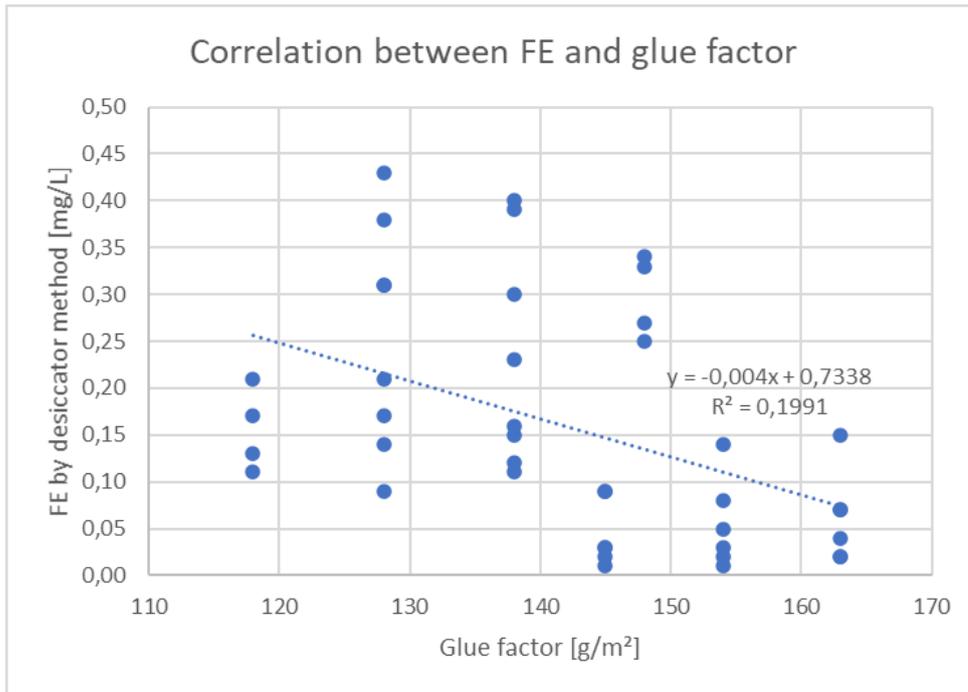


**Figure 1.** Correlation between FE and glue factor, desiccator method.

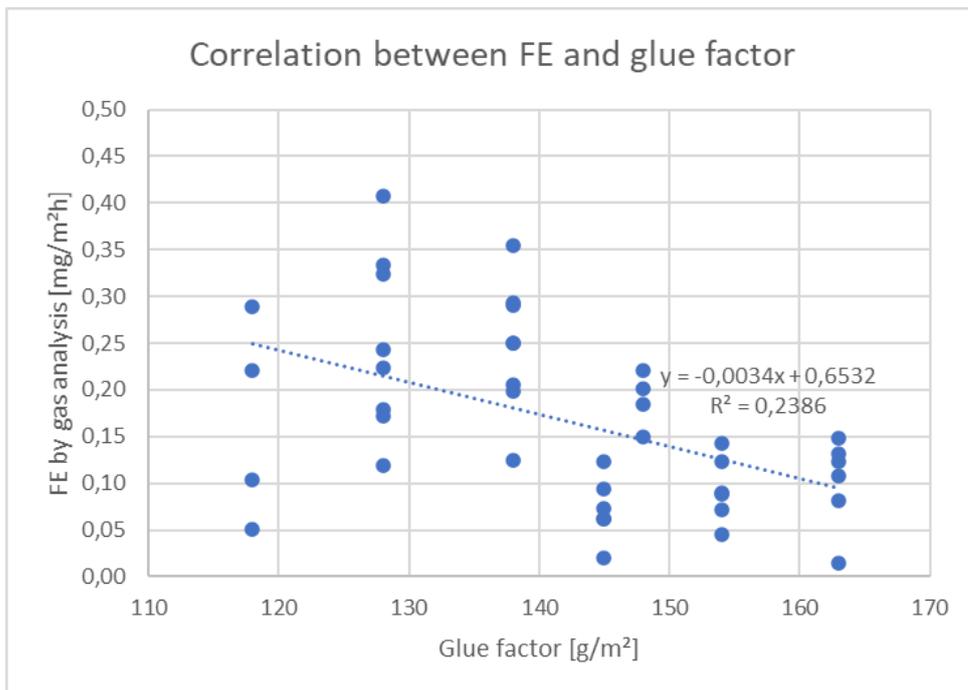


**Figure 2.** Correlation between FE and glue factor, gas analysis.

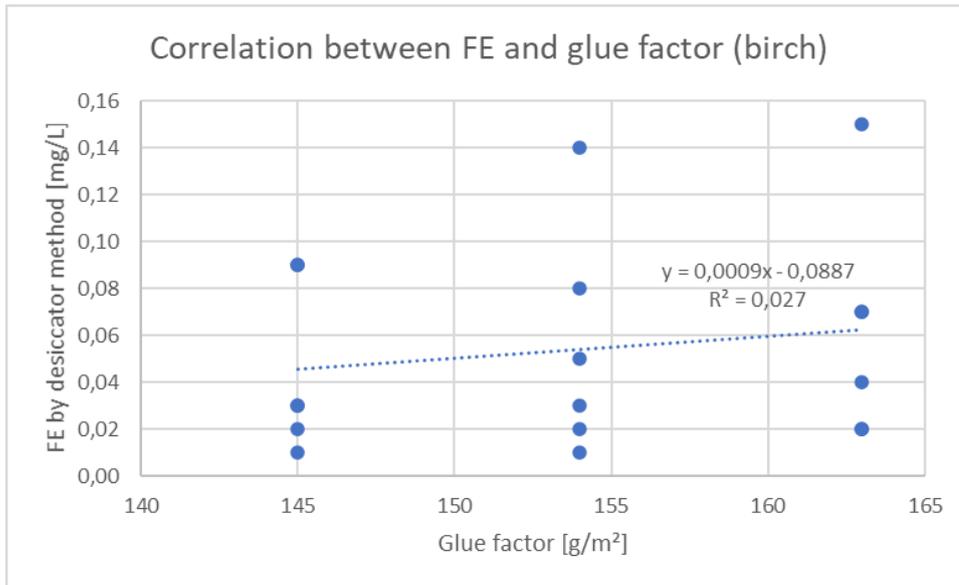


**Figure 3.** Correlation between FE and glue factor (birch), desiccator method.

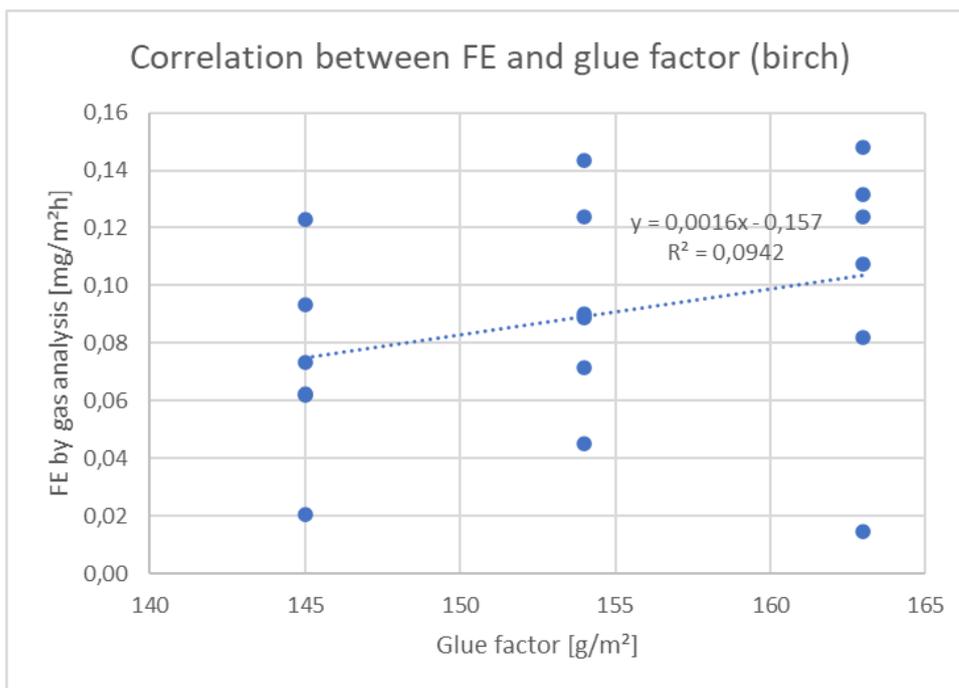


**Figure 4.** Correlation between FE and glue factor (birch), gas analysis.

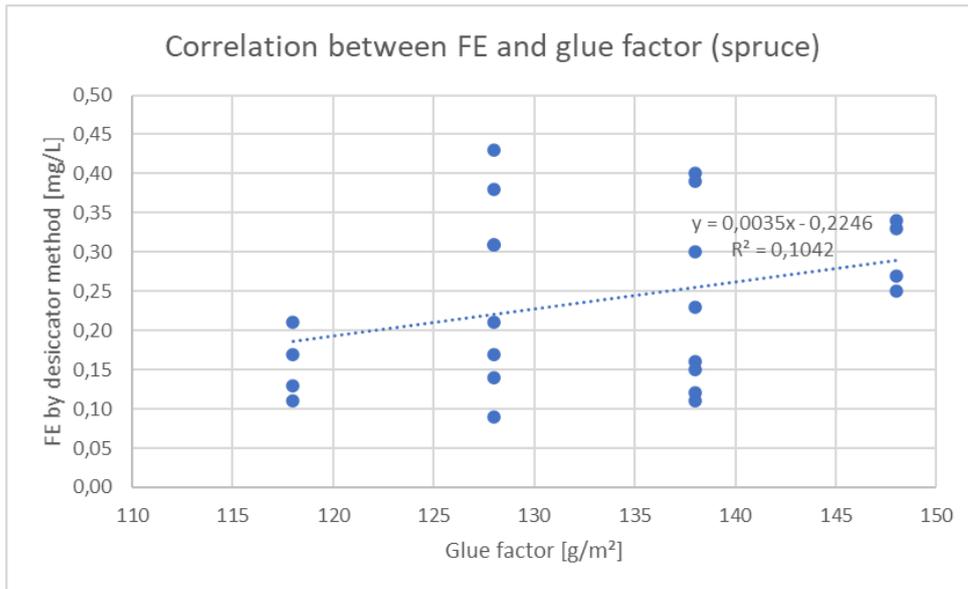


**Figure 5.** Correlation between FE and glue factor (spruce), desiccator method.

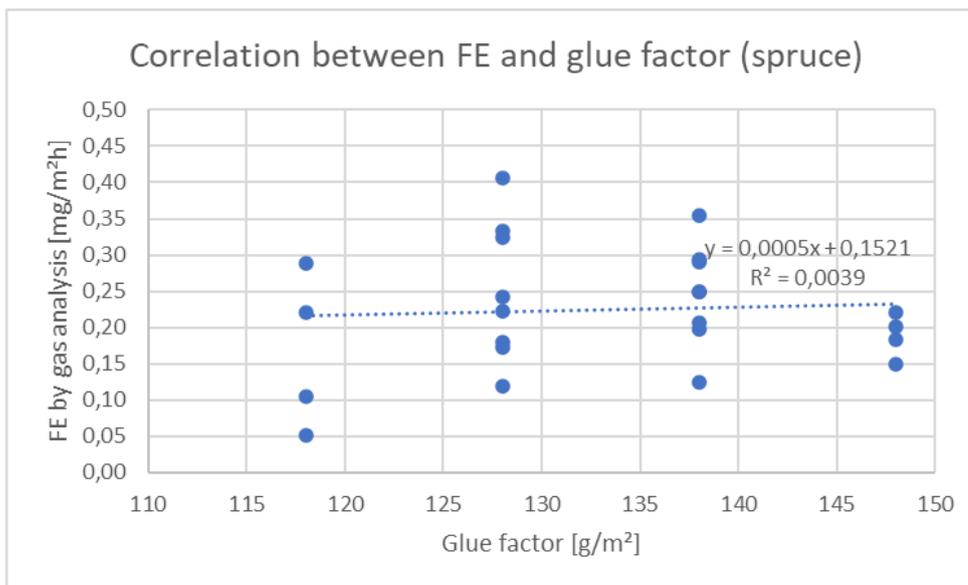


**Figure 6.** Correlation between FE and glue factor (spruce), gas analysis.

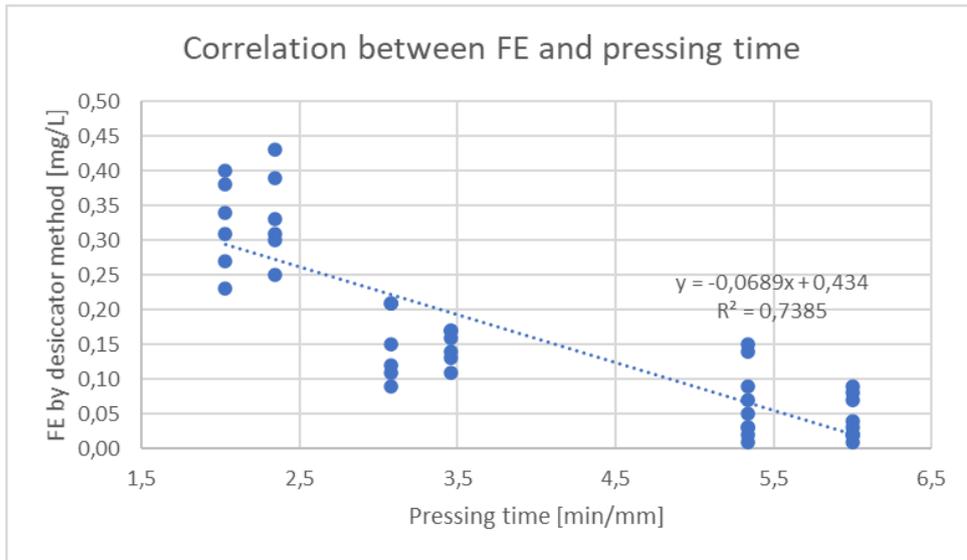


**Figure 7.** Correlation between FE and pressing time, desiccator method.

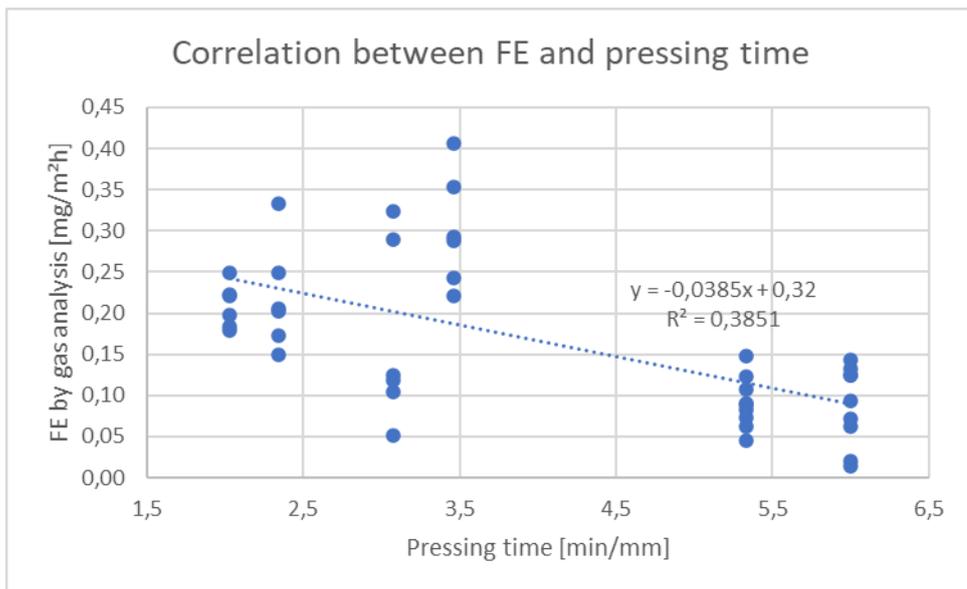


**Figure 8.** Correlation between FE and pressing time, gas analysis.

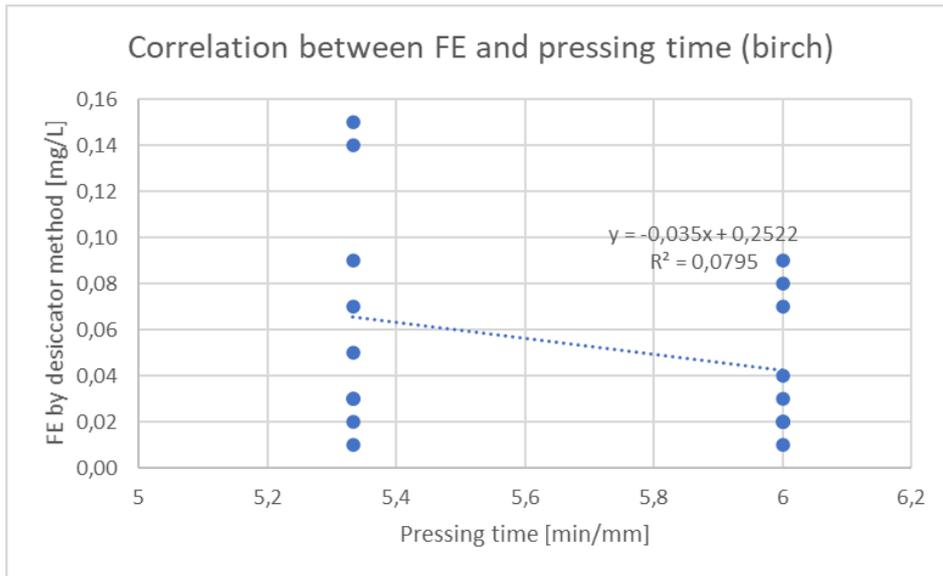


**Figure 9.** Correlation between FE and pressing time (birch), desiccator method.

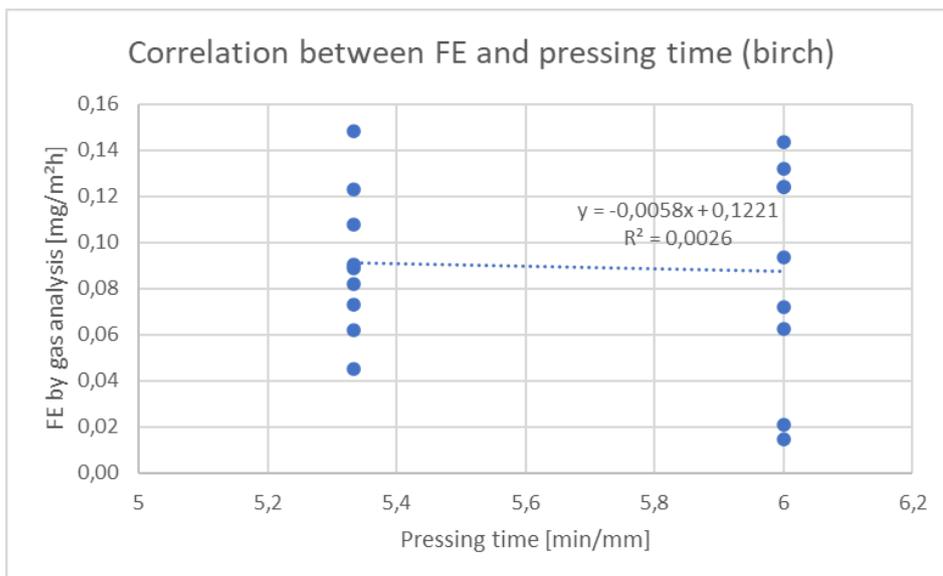

**Figure 10.** Correlation between FE and pressing time (birch), gas analysis.

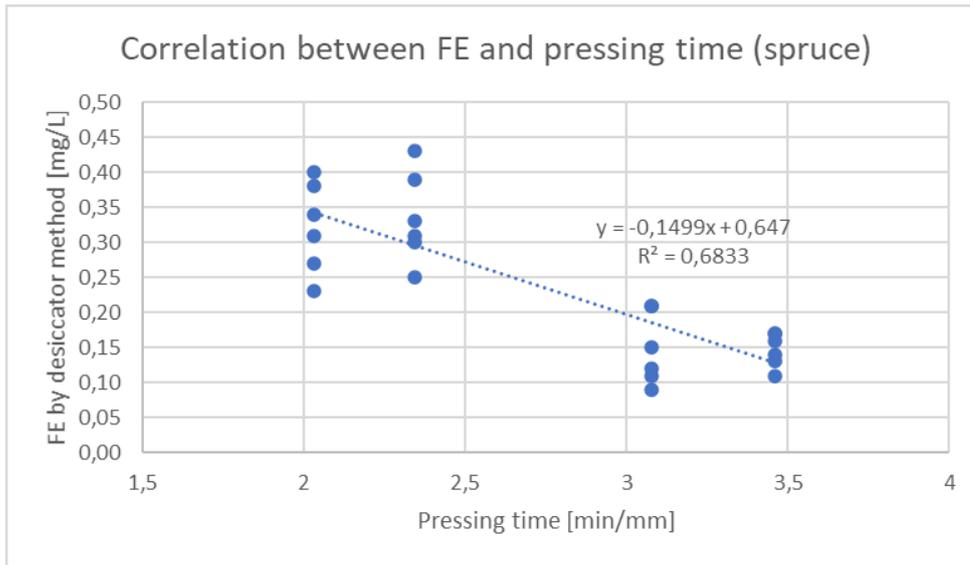

**Figure 11.** Correlation between FE and pressing time (spruce), desiccator method.

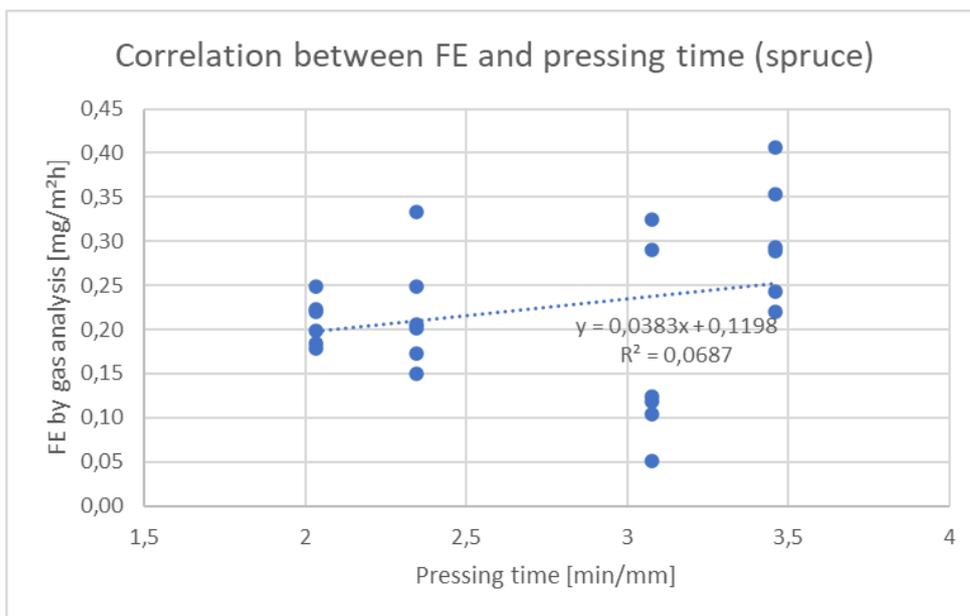

**Figure 12.** Correlation between FE and pressing time (spruce), gas analysis.